



A TOF-SIMS surface chemical analytical study of rare earth element minerals from micro-flotation tests products

S. Chehreh Chelgani*, B. Hart, L. Xia

Surface Science Western, Research Park, University of Western Ontario, London, Ont., Canada N6G0J3

ARTICLE INFO

Article history:

Received 10 November 2012

Accepted 9 January 2013

Keywords:

Rare earth minerals
Flotation
Surface chemistry
TOF-SIMS
SEM-EDX

ABSTRACT

The Thor lake deposit is a world class resource of rare earth (REE) metals and minerals in Canada. Development work to optimize a REE mineral recovery process flow sheet is underway, however, given the ore mineralogy; the developed reagent scheme is relatively complex. As part of a research project, micro-flotation tests were conducted on a feed sample in order to examine factors affecting stream partitioning. SEM-EDX was performed to evaluate variability in grain composition between streams (concentrate and tails) and TOF-SIMS surface analysis was used to determine statistically significant differences in surface species particularly related to potential activation (or depression) of the examined mineral phases. SEM-EDX analysis reveal that the concentrate has a significantly higher proportion of REE bearing grains (carbonates and phosphates) relative to the tail (almost none were identified). Spectral fingerprinting by TOF-SIMS has allowed for the identification of all reagent species investigated. Reagent signal intensity discrimination on test stream mineral surfaces was observed by the TOF-SIMS analysis using reagents at plant concentration levels. TOF-SIMS analysis confirmed that REE bearing grains reporting to the concentrate are doing so in response to collector attachment whereas grains reporting to the tail are doing so in response to a lack of collector and/or in combination with the presence of the depressant. The surface analysis of gangue phases reveal a similar reagent discrimination; the signal intensity of collector species was significantly higher on the concentrate samples relative to the tails while depressant species were significantly enriched on the surface of the gangue phases in the tail samples. A detailed evaluation of the surface species representing the various reagents used in flotation scheme revealed a distinct competitive relationship between two of the reagents. The surface analysis identified that when used in concurrently, there appears to be a negative feedback resulting in a significant reduction in loading for several of the collectors on grains reporting to the concentrate. An evaluation of the effect of reagents on REE mineral in pilot plant is currently under way.

© 2013 Elsevier Ltd. All rights reserved.

1. Introduction

Starting in 1976, the Thor lake property (TLP) has been explored by a number of companies for Rare Earth Elements (REEs), Niobium and Tantalum. In the TLP deposit heavy rare earth elements (HREEs) are present in fergusonite ((Y, HREE)NbO₄) and zircon (ZrSiO₄), whereas the light rare earth elements (LREEs) are present in bastnaesite (Ce, La)CO₃F, synchysite Ca(Y, Ce)(CO₃)₂F, allanite (Ce, Ca, Y)₂(Al, Fe³⁺)₃(SiO₄)₃(OH) and monazite (Ce, La, Nd, Th)PO₄. Niobium and Tantalum are hosted in columbite (Mn, Fe²⁺)(Nb, Ta)₂O₆ as well as fergusonite. It is estimated that the property contains a REE mineral reserve of 12 million tonnes. The final products from processing will include a mixed rare earth oxide concentrate, a zirconium oxide concentrate, a niobium oxide concentrate, and a tantalum oxide concentrate (Paul et al., 2009; Cox et al., 2010).

* Corresponding author.

E-mail addresses: sos4552@gmail.com, Schehreh@uwo.ca (S. Chehreh Chelgani).

Previous investigations indicated that separation of rare earth minerals from oxide and silicate gangue minerals has been successfully carried out by flotation (Abeidu, 1972; Pavez and Peres, 1993, 1994; Cheng et al., 1993; Cheng and Holtha, 1995; Ren et al., 2000, 2009; Chen et al., 2005). Numerous open circuit and locked cycle flotation tests along with pilot plant testing on the TLP samples indicates that at a d_{80} of $-38 \mu\text{m}$ Total Rare Earth Oxide (TREO), ZrO₂, Nb₂O₅ and Ta₂O₅ recoveries can be in the order of 80%. Recoveries in the following proportions are indicated: 90% of the zirconium oxide, 69% of the niobium oxide and 63% of the tantalum oxide to a flotation concentrate (Cox et al., 2010).

In flotation separation, surface chemistry is the principle determinant for selective separation of the various minerals. For that reason, understanding of the factors operating on the surface of REE minerals will potentially provide opportunities for modifying the flotation scenarios, promoting improved selectivity and discrimination of the value and non-added value minerals to selective streams. Measuring surface chemical variability between phases

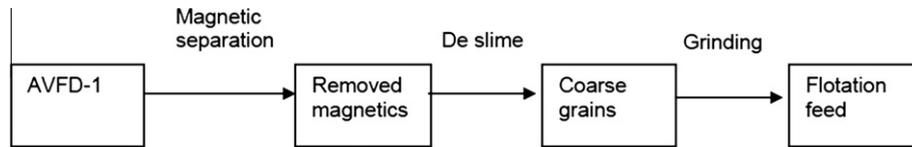


Fig. 1. Sample preparation prior for flotation. Final flotation feed; P80 = 75 μm .

Table 1
Reagents and mass positions used for identification.



Flotation agent	Name	Components	Peak identifiers (mass, amu)
Conditioner (depressant)	Silica/Fe aerosol	Sodium silicate	SiO, SiO ₂ , SiO ₃
		Ferrous chloride, HCl	FeO
Depressant	MLC6 (R4)	Acumer 9400	102
		Alcomer 74A	119
		Alginic acids	283
Modifying agents (depressant)	MX3	Oxalic acid, citric acid, lactic acid	195, 216
			265, 293
Collector	KBX36 (R5)	Phosphoric acid ester	S CNO, SO ₃
		Alkylsulfate sodium	152, 154
		Xylere sulfonate	208, 210
		Alkyl succinamate	266, 268

and stream products can be realized by time of flight secondary ion mass spectrometry (TOF-SIMS). The analytical technique is surface-sensitive, capable of sub monolayer analysis with parts-per-million (ppm) sensitivity (Chryssoulis et al., 1995; Nagaraj and Brinen, 1996, 1997, 2001; Smart et al., 2000, 2006; Piantadosi et al., 2000; Piantadosi and Smart, 2002; Hart et al., 2006; Biesinger et al., 2007).

The Time of Flight Secondary Ion Mass Spectrometer (TOF-SIMS) is unique in that, it measures the outermost atomic layers of any material. In this regard, the technique is particularly suited

for the analyses of surface chemistry on materials from a variety of mineral processing applications. The TOF-SIMS technique utilizes an energetic primary ion beam to sputter (remove) and ionize small amounts of the sample surface including material adsorbed onto the sample surface. These generated secondary ion yields (SIY) are subsequently analyzed in a time-of-flight mass spectrometer that capable parallel detection of all mass species originating from the surface (Hart et al., 2006; Smart et al., 2006).

The purpose of this study is to analyze the surface of particles with specific relation to the various reagents currently being evaluated for the flotation of REE minerals in pilot plant trials. The study, through micro-flotation testing and surface chemical analyses, measures the relative difference in reagent(s) on value and non-value particle surfaces from test stream products in order to potentially better understand the factors affecting particle partitioning. The approach was to: (i) evaluate the capacity of the TOF-SIMS to correctly identify the various reagents and (ii) measure reagent differences on micro-flotation test stream products. The testing was performed on feed samples to the pilot plant. Scanning electron microscopy coupled with energy dispersive X-ray spectroscopy (SEM-EDX) was used to get a general idea of the micro-flotation tests separation efficiency and to evaluate particle composition and liberation. The data may provide some insight to surface chemical controls operating on the REE oxides and associated minerals. This study is part of a larger investigation focused on evaluating the capacity of the TOF-SIMS to analyze the surface of various value added oxide phases with the aim of modeling molecular interactions of reagents and the REE mineral surface under specific conditions. To our knowledge this investigation is the first application of TOF-SIMS on REE mineral flotation separation.

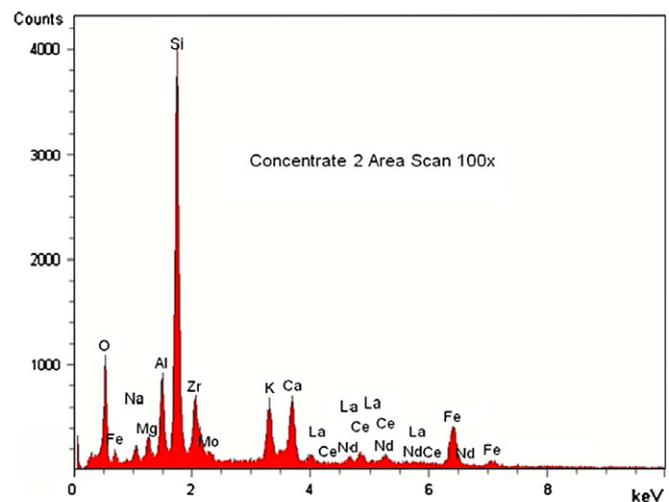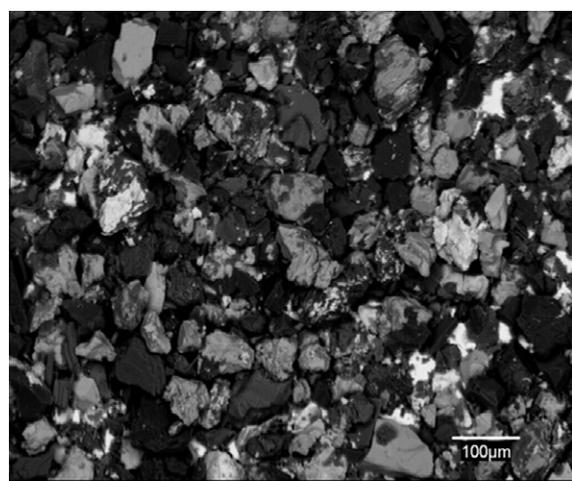

	O	Na	Mg	Al	Si	K	Ca	Fe	Zr	Mo	La	Ce	Nd
Con 2 area scan	47.7	1.3	1.2	3.7	19.0	4.0	4.6	7.9	5.7	0.5	0.9	2.4	1.3

Fig. 2. Concentrate sample. Back scattered electron image (BSE), EDX spectra and semi-quantitative elemental analysis of the entire area in the image. In the BSE image grain brightness is a reflection of the grains average atomic number; brighter grains having elements with higher atomic numbers. The very bright grains in the above BSE image are identified as sulphides, zircons and rare earth element containing minerals. The remainder of the grains is primarily silicates of various compositions along with Fe oxides. Note: REE peaks are clearly identified in the spectra with composition provided in Table 1.

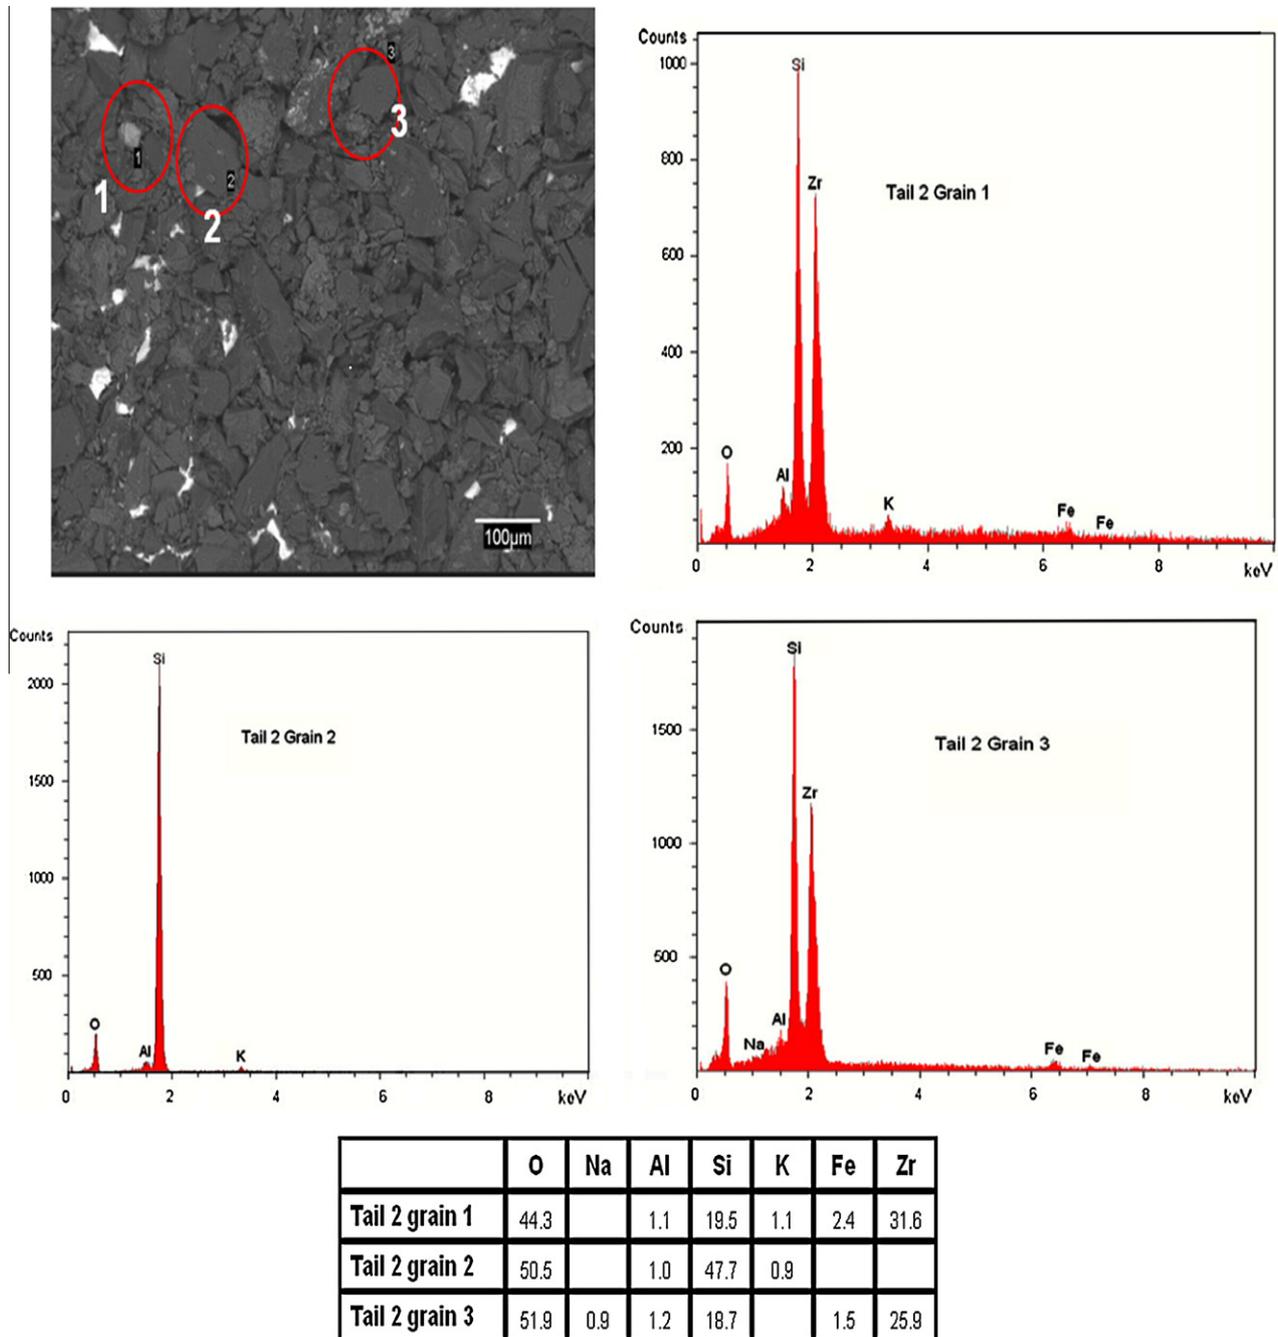


Fig. 3. Tail sample, BSE image, EDX spectra and semi-quantitative elemental analysis of selected grains in the image. The numbers in the image correspond to the spectra and data in the table. All data in wt.%. In the BSE image grain brightness is a reflection of its average atomic number; brighter grains having elements with higher atomic numbers. The binary phase outlined in the red circle is an aluminosilicate with mixed zircon grains similar in composition to grain 3.

2. Experimental methodology

Samples were obtained from the Thor lake deposit. Several micro-flotation tests were performed on samples in order to understand the reaction between reagents (collectors, and depressants) and rare earth minerals during flotation. Prior to flotation the feed sample was prepared in order to remove magnetics and de-slime (Fig. 1). For the micro-flotation test, 5 g of the flotation feed was conditioned for 10 min at a pH of 6.5 (controlled by silica/Fe aerosol) to which the appropriate level of reagents listed in Table 1 were added followed by several minutes of further conditioning. The mixture was then transferred to a 100-ml Siwek-type flotation cell (Siwek et al., 1981) and 0.05-ml MIBC as frother was added.

Airflow rate was 0.76 ml/min and the flotation time was 5 min. The float and non-float products were collected and immediately frozen in order to preserve their surface chemical characteristics.

The resulting samples were examined by SEM–EDX in order to get some idea of the separation efficiency. A separate sample was analysed by the TOF-SIMS to identify the loading characteristics of selected reagents on the surfaces of mineral grains reporting to the concentrate and tails.

2.1. Analytical techniques

The instruments used in this work are an ION-TOF, TOF SIMS IV secondary ion mass spectrometer, and Leo 440 Scanning Electron

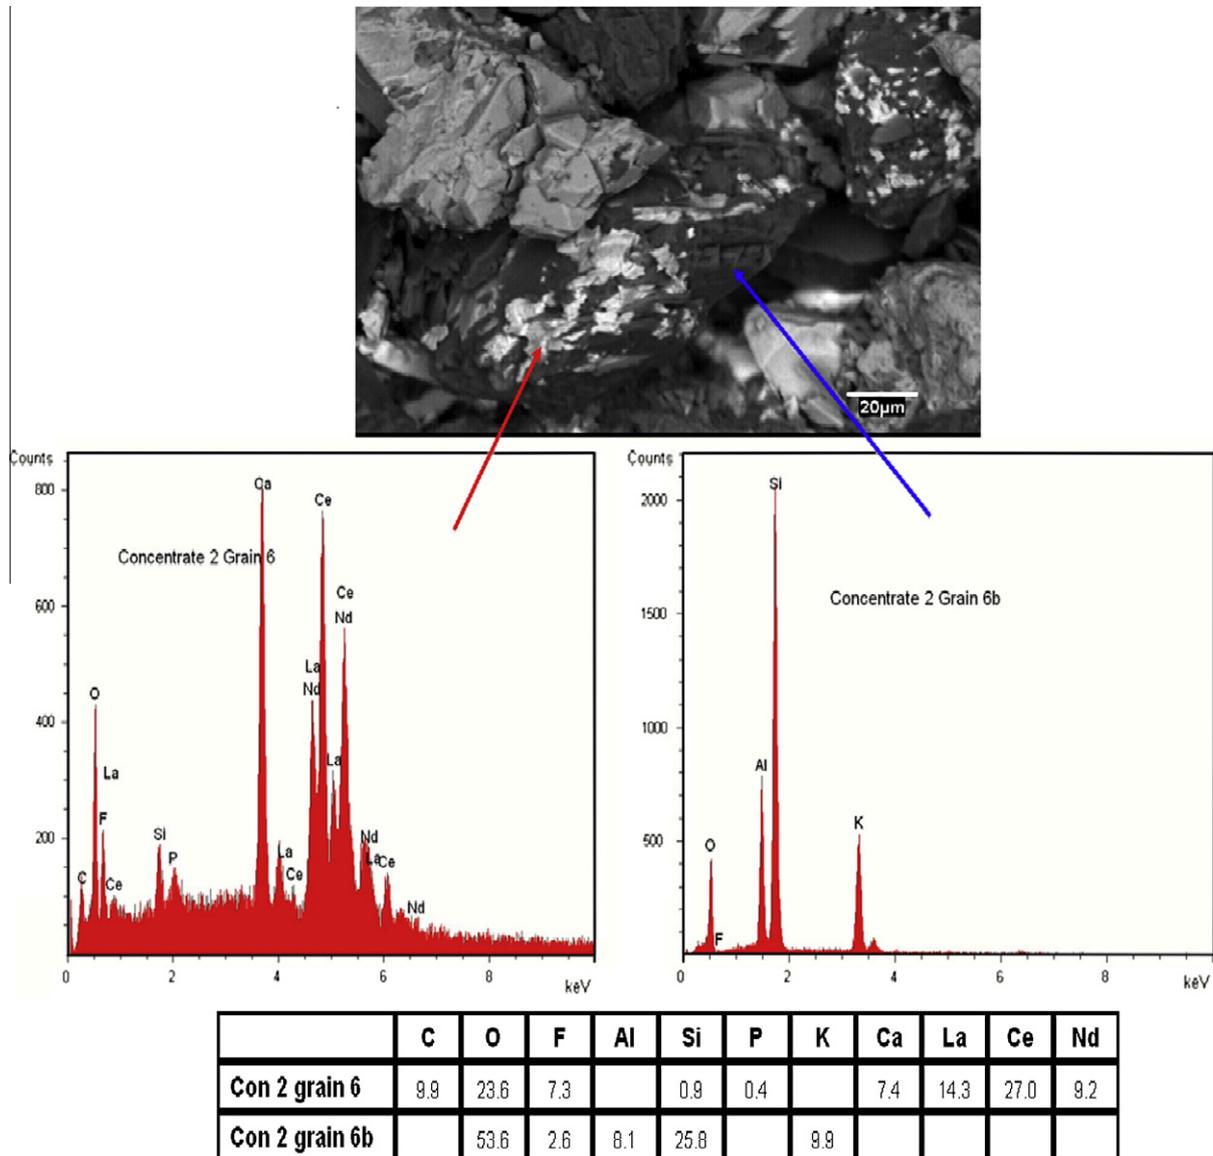


Fig. 4. Concentrate sample. BSE image, EDX spectra and semi-quantitative elemental analysis of a multi-component grain. The grain is composed of a REE oxide (Synesite) and a potassium aluminosilicate. All data in wt%. In the BSE image grain brightness is a reflection of its average atomic number; brighter grains having elements with higher atomic numbers.

Microscope coupled with Energy Dispersive X ray Analysis (SEM–EDX).

TOF-SIMS allows for the analysis of the outermost atomic layers of a surface by mass spectrometry. An isotopically enriched $^{209}\text{Bi}^+$ (Bismuth) primary ion beam is rastered across an area of interest on the sample surface. The raster size used was $\sim 300\ \mu\text{m}$ with an acquisition time of 100 scans. The bombardment of the surface with the bismuth primary ion beam induces the emission of positively and negatively charged secondary ions from the sample surface. These secondary ions are extracted from the sample surface and mass analysed using a time-of-flight mass spectrometer. A plot of secondary ion intensity versus mass results in a traditional first order mass spectrum, with a resolution of 10,000 above 200 atomic mass units (amu). TOF-SIMS can detect species with concentration in the ppm range. The data were recorded with full mass spectra in 256×256 pixels using a hybrid focussed bunched mode $^{209}\text{Bi}^{3+}$ -cluster ion beam. Sample charging was neutralized with an electron flood gun.

Along with the TOF-SIMS analyses the samples were examined using scanning electron microscopy (SEM) coupled with energy

dispersive X-ray spectroscopy (EDX). Routine EDX analyses can detect all elements from carbon through to uranium, with a minimum detection limit of approximately 0.5 wt%. The samples were given a thin, carbon coating prior to the analysis in order to alleviate charging problems during the SEM examination. The brief examination was performed in order to evaluate the matrix composition of grains present in the samples. Selected areas from the flotation samples were examined (approximately $700 \times 500\ \mu\text{m}$ regions) and provide some crude information regarding the separation efficiency. Individual grains were analysed for composition and X-ray intensity maps provide some information regarding the distribution of selected elements and hence grains of interest.

2.2. Data treatment

All raw spectra were processed using the IONTOF software. Peaks in the calibrated spectra were assigned to specific isotopes in accordance with their atomic mass unit (amu) and similarly peaks reflecting molecular species of the collector were assigned mass positions. The corrected ion intensity for each mass position,

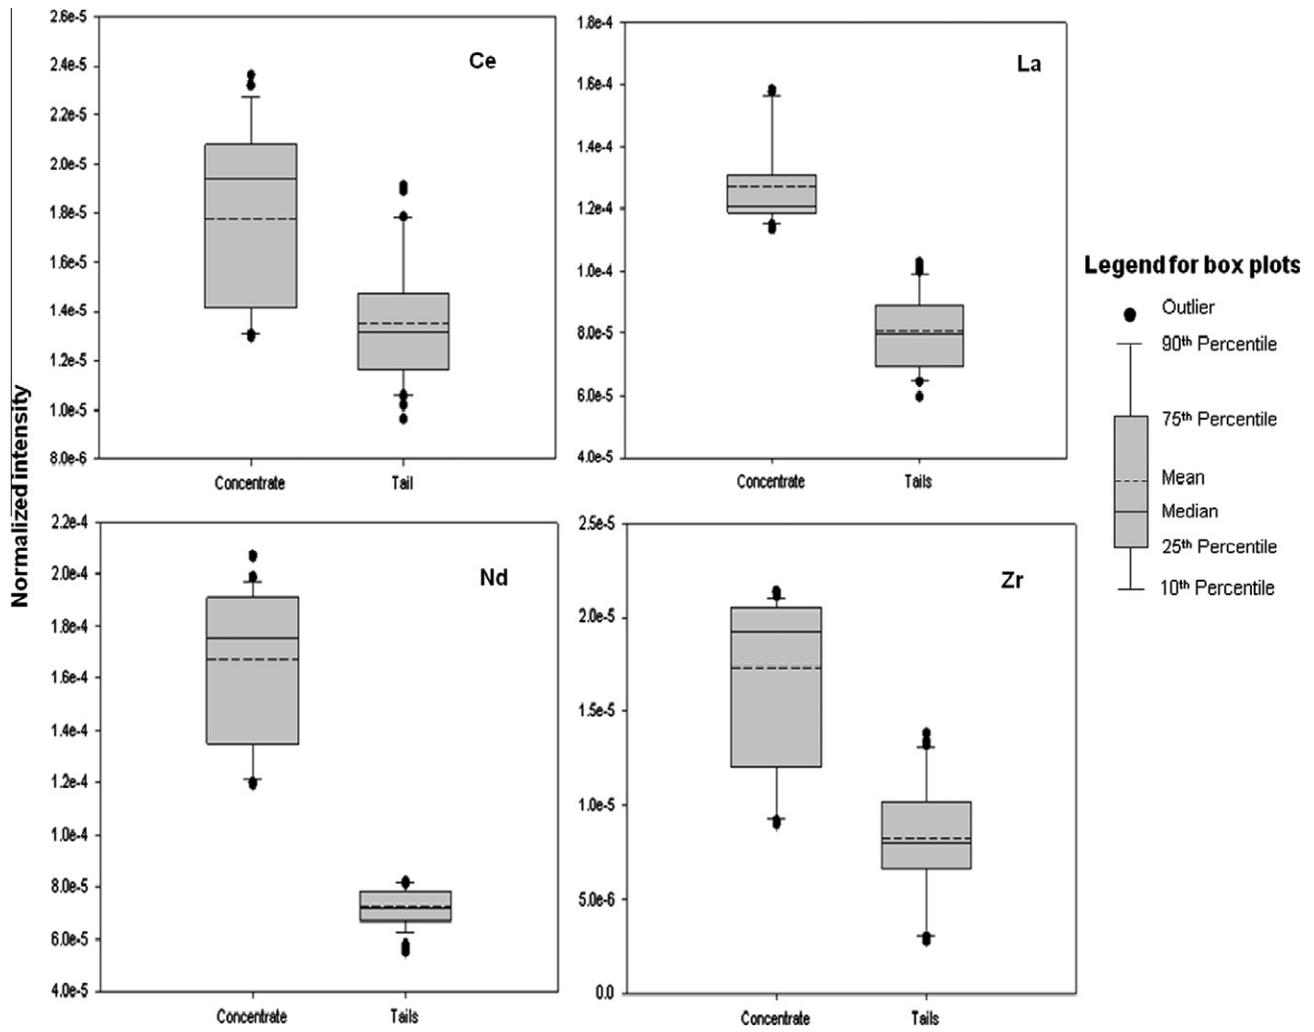


Fig. 5. Box plots showing the normalized intensity for Nd, Ce, La and Zr on grains from micro-flotation test concentrate and tails samples.

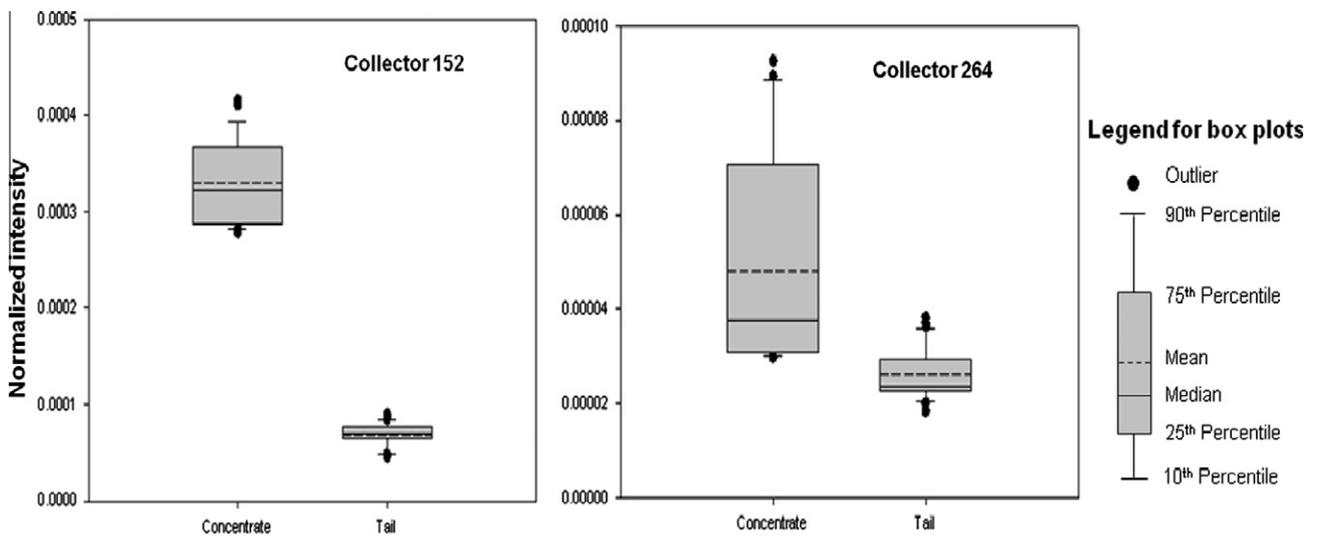


Fig. 6. Box plots showing the normalized intensity collector peaks 152 and 264 on grains from micro-flotation test concentrate and tails samples.

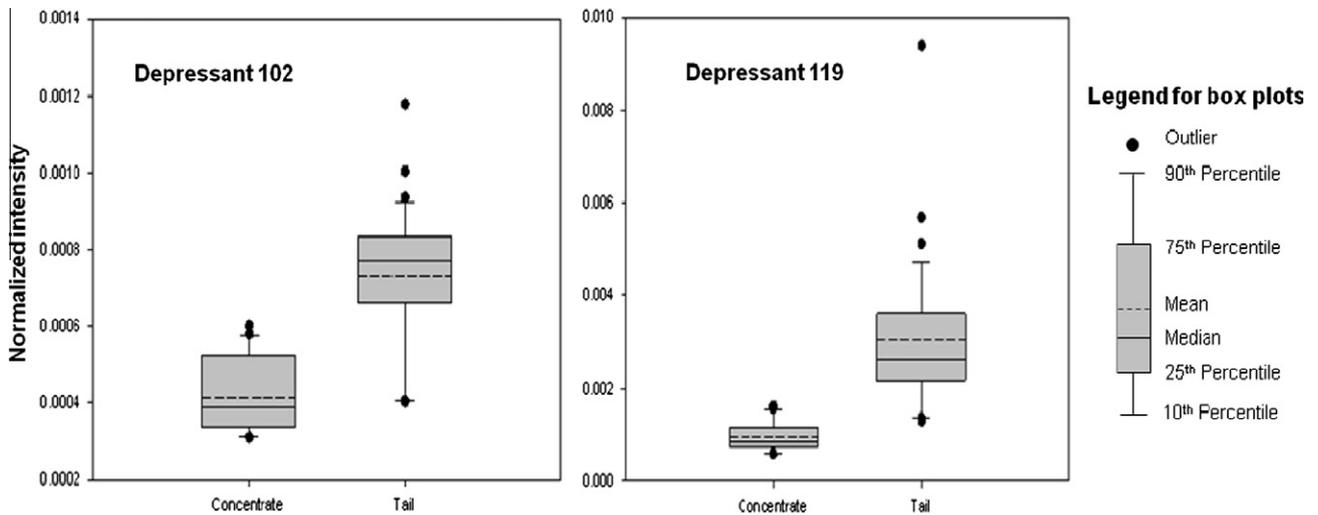


Fig. 7. Box plots showing the normalized intensity for depressant (MLC-6) peaks 102 and 119 on grains from micro-flotation test concentrate and tails samples.

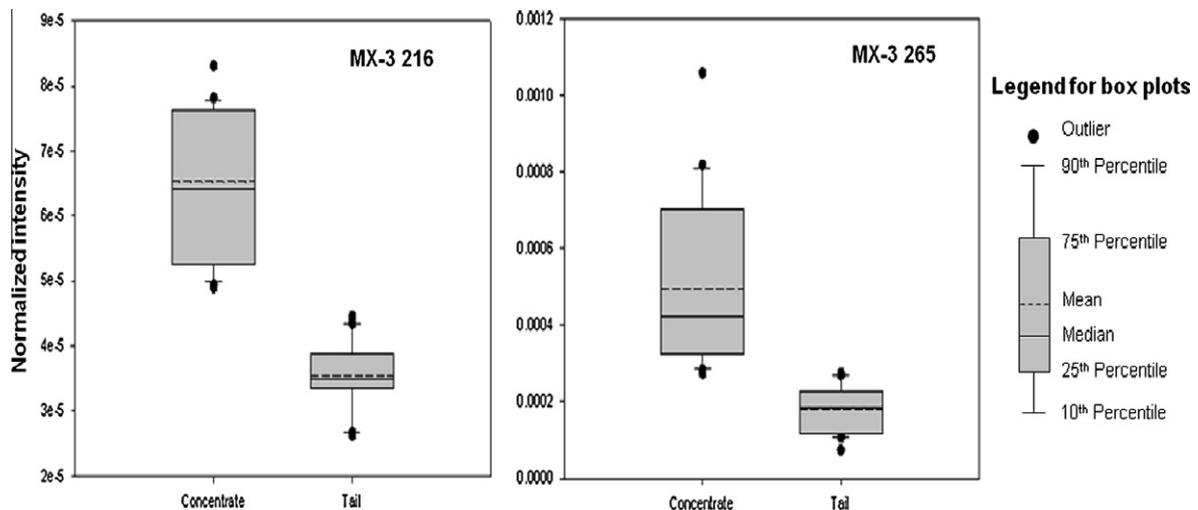


Fig. 8. Box plots showing the normalized intensity for conditioner peaks 216 and 265 on grains from micro-flotation test concentrate and tails samples.

measured as the integrated area under each peak corrected for dead times can be related to abundance of the particular specie. In order to compare intensities between areas of different dimensions, corrected intensities were normalized to the total number of counts for the areas examined.

The analysis provides a comprehensive survey of the surface species on the mineral grains in the various samples. The analytical approach was to conduct comparative surface analyses of the provided samples in order to determine statistically significant differences in the surface composition of species particularly related to potential activation (or depression) of the examined mineral phases (there was no attempt to discriminate grain types during the analysis).

3. Results

3.1. SEM-EDX

The SEM/EDX analysis of the concentrate and tail samples provides a rough evaluation of the flotation test performance. Large area analysis of the concentrate samples shows significantly higher concentrations of La, Ce and Nd relative to the tail samples where

none of those elements were identified (Figs. 2 and 3). REE containing grains are tentatively identified (based on EDX data only) as monazite, allenite and synchysite. Other minerals examined include zircon, pyrite along with gangue aluminosilicate phases. Zircon was the only REE bearing mineral phase identified in the tail sample (Fig. 3). The simplified evaluation indicates that the flotation separation was very successful, as almost no REE grains were identified in the tail sample. The back scattered electron (BSE) images suggest that many of the minerals of interest are not well liberated and that in a number of instances the REE phases occur disseminated throughout a silicate host (Fig. 4).

3.2. TOF-SIMS

All TOF-SIMS data presented (counts) are normalized by the total ion intensity (counts of the recorded total mass spectrum) for the region of interest. The normalized intensity data are plotted in vertical box plots and illustrate relative changes in surface specie abundance for the mineral grain examined in the sample. Comparative analyses are discussed in relation to the reported median normalized intensity value for the individual data sets. It should be noted that the TOF-SIMS analysis reported here is for undifferenti-

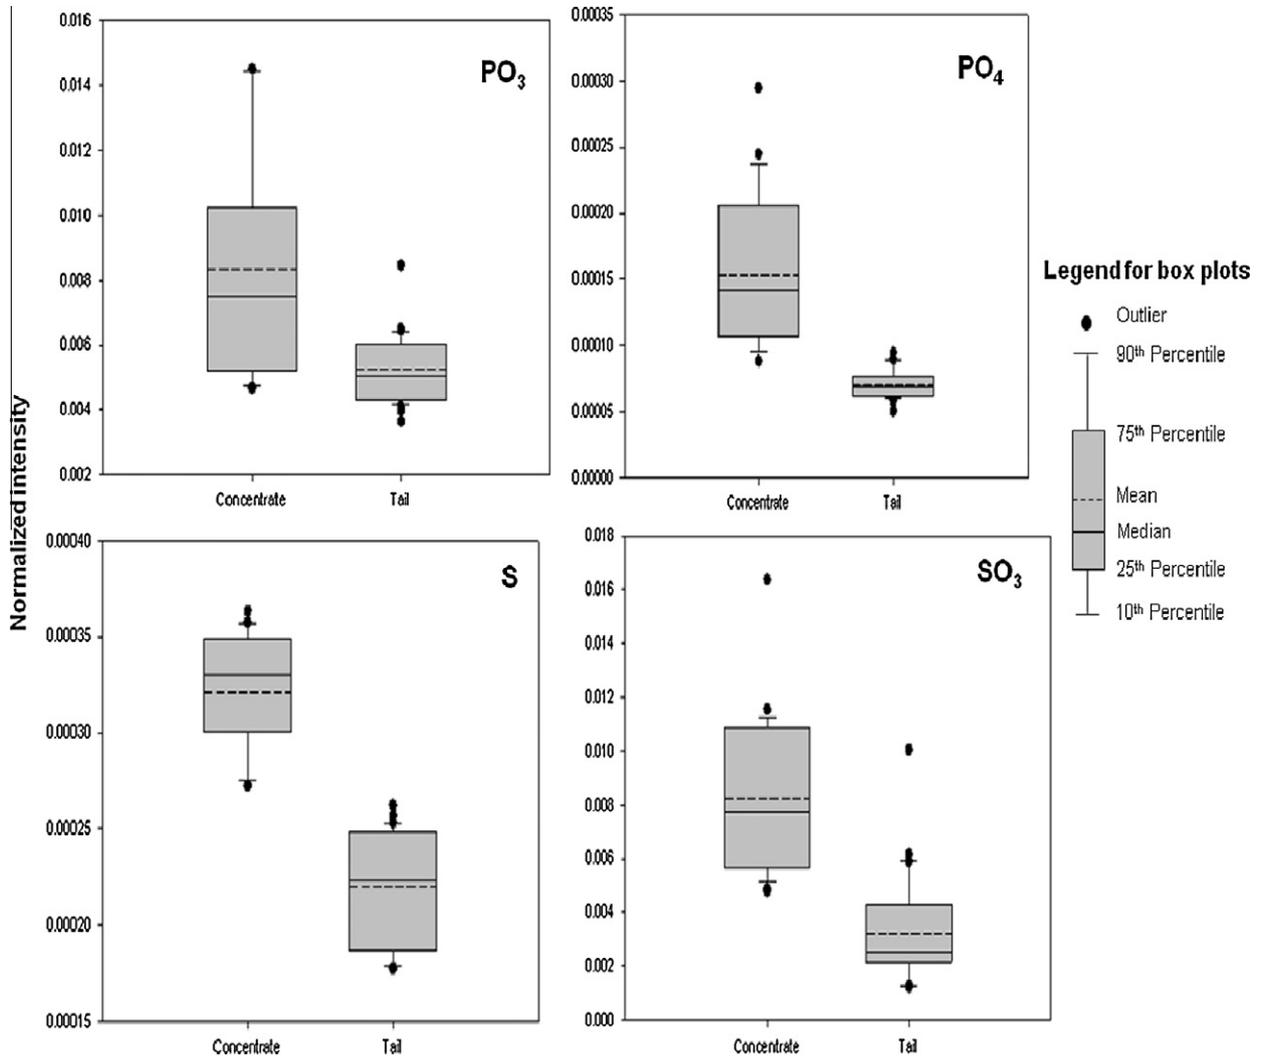


Fig. 9. Box plots showing the normalized intensity PO_3 , PO_4 , S and SO_3 on grains from micro-flotation test concentrate and tails samples.

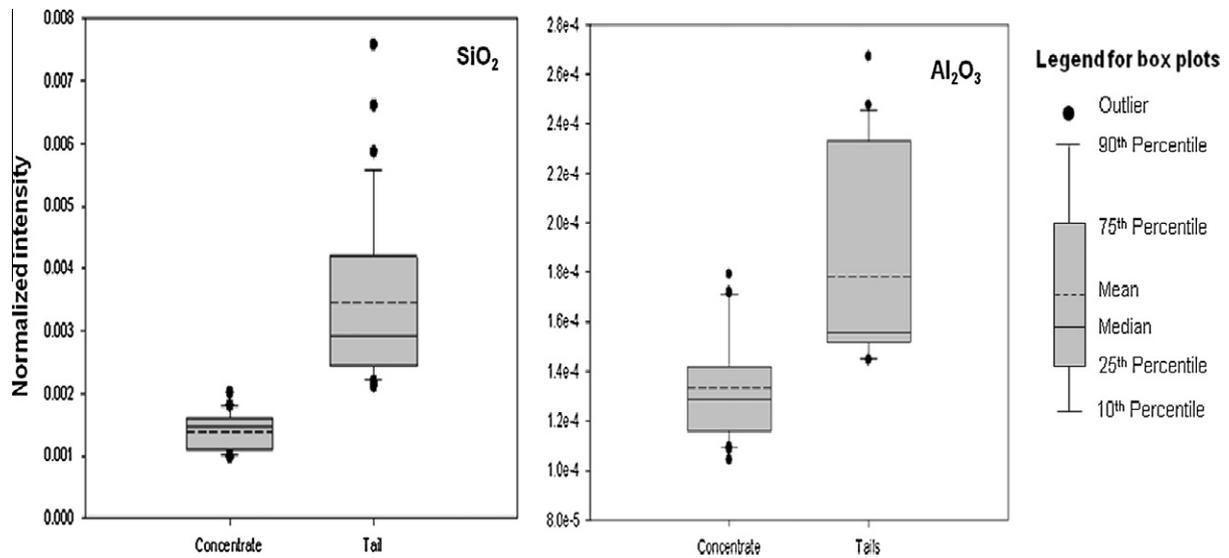


Fig. 10. Box plots showing the normalized intensity for SiO_2 and Al_2O_3 on grains from micro-flotation test concentrate and tail samples.

ated grains. The data therefore will be partially biased towards surface characteristics representative of gangue grains relative to REE

bearing grains as there is a greater proportion of those grains in the samples analysed.

Prior to the analysis of the samples the various reagents used in the flotation scheme were deposited on a silicon substrate and analysed by TOF-SIMS in order to generate spectral fingerprints for each reagent. The dominant peak positions (molecular fragments) for the reagents examined are given in Table 1. The mass positions of these peaks were used to identify the presence of the reagents and assess variations in loading between different grains in each of the samples investigated.

These results of the grain surface analysis from the flotation test indicate that the normalized intensity of Ce, Nd, La and Zr is significantly higher on the grains analysed from the concentrate sample (Fig. 5). Intensities of peaks representative of the collector KBX-36 (152, 154, 264 and 266 amu) are higher on the grains from the concentrate (Fig. 6) while peaks representative of the depressant MLC-6 (mass positions 102 and 119) are higher on the grains from the tail sample (Fig. 7). The intensity of the conditioner MX-3 (peaks at 195, 216, 265 and 293 amu) are also higher on the grains from the concentrate (Fig. 8). The normalized intensity of PO₃ and PO₄, S and SO₃ are significantly higher on the grains analysed from the concentrate sample (Fig. 9). The normalized intensity of SiO₂ and Al₂O₃ are significantly higher on the grains analysed from the tail sample (Fig. 10).

4. Discussion

In this investigation, the grains were not differentiated with respect to matrix composition. The normalized surface intensity of the REE elements Ce, Nd and La along with Zr reflects the greater proportion of REE bearing mineral phases and zircon reporting to the concentrate relative to the tails. With sulphide flotation some degree of element transfer between phases is commonly observed in surface chemical analyses. The best example of this is the transfer of Cu from bornite, chalcocite or chalcopyrite to sphalerite (Chandra and Gerson, 2009). For this test, given the relative low solubilises of the REE containing minerals in the samples, it is unlikely that any significant transfer of REE elements between phases would be observed and therefore the mass intensities observed on the surface of grains are most likely related to the mineral composition. This agrees well with the SEM-EDX evaluation of the concentrate and tail samples which showed a significantly greater proportion of REE mineral phases in the concentrate sample while the grains in the tail are predominantly silicates.

From the surface analysis, species identified as representative of the collectors indicate that phases reporting to the concentrate do so in response to collector adsorption. This is irrespective of grain composition, it would appear that both the REE phases and some of the gangue phases report to the concentrate in response to collector loading. The presence of the collector on these phases is also supported by the higher intensities of sulphur and phosphate species reflective of the sulfonate and the phosphoric acid ester collectors found in the KBX36 reagent mix.

Surface analyses indicate that the grains reporting to the tail show lower collector loadings while containing a greater proportion of depressant (MLC-6) on their surfaces. The higher proportion of Si and Al species on grains from the tails may be related to their matrix composition. The SEM/EDX evaluation reported a greater proportion of grains in the tails are silicates. An alternative explanation to the Si enrichment on the grains from the tails may be related to the addition of the modifier Na-silicate which due to surface attachment may also be performing as a depressant.

There is a curious enrichment of the MX-3 species on the surface of the grains from the concentrate. It may be related to differences in surface reactions between by the components in MX-3 with the phosphates and carbonates (identified in greater proportion in the concentrate) relative to the silicates. One possible expla-

nation may be related to their ability to complex with various positive surface ions. For the silicates, interaction with the organic acids involves surface modification by a chelating effect. The soluble chelated specie is subsequently removed from the mineral surface, consistent with the surface chemical data, which in turn blocks or controls the action of metal ions causing depression in part, by not allowing collector attachment. On the surface of REE bearing carbonates or phosphates, the action of exposed ions may significantly more difficult to control. The interaction of organic acids with positively charged exposed surface ions, for example Ca, La, Ce, may result in the formation of a complex rather than a chelate. While still soluble, the data suggests that there does not appear to be significant removal of surface ions, nor is the activity of the surface species significantly reduced by the metal ion-acid complex. Given the distribution of the collector species, viz. much higher intensities on grains in the concentrate, the presence of MX-3 does not appear to interfere with the flotation process.

5. Conclusion

5.1. Based on the micro-flotation tests

SEM-EDX analysis of concentrate and tails sample grains from the micro-flotation test reveal that the concentrate has a significantly higher proportion of REE bearing grains (carbonates and phosphates) relative to the tail (where almost none were identified). SEM-EDX analyses also indicate that many of the minerals of interest are not well liberated and that, in a number of instances, the REE phases occur disseminated throughout a silicate host. Surface analyses of concentrate and tails sample grains from micro-flotation tests with the TOF-SIMS reveals that grains reporting to the concentrate are doing so in response to collector attachment. The grains reporting to the tail are responding to a lack of collector and/or in combination with the presence of the depressant. Factors controlling the discrimination of the collectors may be related to the presence of surface exposed REE along with the action of the modifying agent MX-3. Along with the presence of the depressant in the grains from the tails, there is also some suggestion that their discrimination to the tails may be facilitated by the addition of the Na-silicate.

Acknowledgement

This work was partially completed with funding provided by the Natural Sciences and Engineering Research Council of Canada (NSERC Grant # EGP 428425-11). The authors would like to thank Avalon Rare Metals Inc. for allowing us to publish this information.

References

- Abeidu, A.M., 1972. The separation of monazite from zircon by flotation. *Journal of the less-common metals* (29), 113.
- Biesinger, M.C., Hart, B., Polack, R., Kobe, B.A., Smart, R., St. C., 2007. Analysis of mineral surface chemistry in flotation separation using imaging XPS. *Minerals Engineering* 20 (2), 156.
- Chandra, A.P., Gerson, A.R., 2009. A review of the fundamental studies of the copper activation mechanism for selective flotation of sulfide minerals, sphalerite and pyrite. *Advances in Colloid and Interface Science* 145, 97.
- Chen, G.L., Tao, D., Ren, H., Ji, F.F., Qiao, J.K., 2005. An investigation of niobite flotation with octyldiphosphonic acid as collector. *International Journal of Mineral Processing* (76), 111.
- Cheng, T., Holtha, P.N., 1995. The particle detachment process in flotation. *Minerals Engineering* 8 (8), 883.
- Cheng, T., Holtha, P.N., Tran, T., 1993. Froth flotation of monazite and xenotime. *Minerals Engineering* 6 (4), 341.
- Chryssoulis, S., Stowe, K., Niehus, E., Cramer, H.G., Bendel, C., Kim, J., 1995. Detection of collectors on mineral grains by ToF-SIMS. *Transactions of the Institute of Mining and Metallurgy, Section C. Mineral Processing and Extractive Metallurgy* (104), C117.

- Cox, J.J., Moreton, Ch., Goode, J.R., Hains, D.H., 2010. Technical Report on the Thor Lake Project, Northwest Territories, Canada. pp. 1–350.
- Hart, B., Biesinger, M., Smart, R., St, C., 2006. Improved statistical methods applied to surface chemistry in minerals flotation. *Minerals Engineering* 19 (6–8), 790.
- Nagaraj, D.R., Brinen, J.S., 1996. SIMS and XPS study of the adsorption of sulphide collectors on pyroxene: a case for inadvertent metal in activation. *Colloids and Surfaces, A: Physicochemical and Engineering Aspects* (116), 241.
- Nagaraj, D.R., Brinen, J.S., 1997. SIMS analysis of flotation collector adsorption and metal ion activation on minerals: recent studies. *Transactions of the Indian Institute of Metals* (50), 365.
- Nagaraj, D.R., Brinen, J.S., 2001. SIMS study of adsorption of collectors on pyrite. *International Journal of Mineral Processing* (63), 45.
- Paul, J., Stubens, T.C., Arseneau, G., Maunula, T., 2009. Avalon Rare Metals Inc. Thor Lake – Lake Zone Mineral Resource Update, 1–193.
- Pavez, O., Peres, A.E.C., 1993. Effect of sodium metasilicate and sodium sulphide on the floatability of monazite-zircon-rutile with oleate and hydroxamates. *Minerals Engineering* 6 (1), 69.
- Pavez, O., Peres, A.E.C., 1994. Bench scale flotation of a Brazilian monazite ore. *Minerals Engineering* 7 (12), 1561.
- Piantadosi, C., Smart, R.St.C., 2002. Statistical comparison of hydrophobic and hydrophilic species on galena and pyrite particles in flotation concentrates and tails from ToF-SIMS evidence. *International Journal of Mineral Processing* (64), 43.
- Piantadosi, C., Jasieniak, M., Skinner, W.M., Smart, R., St, C., 2000. Statistical comparison of surface species in flotation concentrates and tails from ToF-SIMS evidence. *Minerals Engineering* 13 (13), 1377.
- Ren, J., Song, Sh., Valdivieso, A.L., Lu, Sh., 2000. Selective flotation of bastnaesite from monazite in rare earth concentrates using potassium alum as depressant. *International Journal of Mineral Processing* (59), 237.
- Ren, H., Song, G., Ji, F., 2009. Flotation of niobite, fersmite, and ilmenorutile. *International Journal of Minerals, Metallurgy and Materials* 16 (3), 249.
- Siwek, B., Zembala, M., Pomianowski, A., 1981. A method for determination of fine particle floatability. *International Journal Mineral Processing* (8), 85.
- Smart, R.St.C., Jasieniak, M., Prince, K.E., Skinner, W.M., 2000. SIMS study of oxidation mechanisms and polysulphide formation in reacted sulphide surfaces. *Minerals Engineering* 13 (8–9), 857.
- Smart, R.St.C., Hart, B., Biesinger, M., Francis, J., Negeri, T., 2006. Application of principal component analysis and TOF-SIMS to mineral recognition, surface chemistry and separation by flotation. *Geochimica et Cosmochimica Acta* 70 (18), A597.